

RESEARCH HIGHLIGHT

Has large-scale artificial photosynthesis become real?

Kazuhiro Takanabe

NPG Asia Materials (2016) 8, e326; doi:10.1038/am.2016.171; published online 11 November 2016

Apart from the discussion about whether fossil fuels will be depleted sooner or later or the tremendous impact of the increase in atmospheric CO₂ on the environment, solar energy conversion and utilization is intrinsic to meeting energy demands that have been increasing and will continue to increase in coming years. To achieve this goal, efficient devices and systems have been investigated to achieve artificial photosynthesis, i.e., the use of solar (photon) energy to fuel energetically uphill reactions, such as water-splitting ($\text{H}_2\text{O} \rightarrow \text{H}_2 + 1/2\text{O}_2$). ARPChem, a consortium involving some Japanese universities and several companies sponsored by METI, Japan, has been working on a long-term plan to establish strategic novel processes, including the chemical process of H₂ production from solar energy, followed by CO₂ hydrogenation. The water-splitting project is led by Prof Domen at the University of Tokyo, whose team has achieved the leading solar energy conversion efficiency values by using novel and creative ideas.

The paper published by Wang *et al.*¹ involves a novel device for photocatalytic water-splitting, producing H₂ and O₂ from H₂O using a single photocatalytic sheet. The authors have shown a pathway to move from the laboratory scale toward practical applications, which requires photon collection on a large scale. The successful cogeneration of a mixture of hydrogen and oxygen from pure water was achieved on the basis of varied knowledge accumulated by the authors. A two-step reaction, the so called Z-scheme, using two photocatalysts for H₂ and O₂ evolution, respectively, was achieved, where each photocatalyst was successfully optimized to enhance the evolution of H₂ (SrTiO₃:La,Rh) or O₂ (BiVO₄:Mo). Another critical aspect of the study was the effective suppression of the back reaction (H₂O formation) by two types of surface decoration.^{2,3} Then, these photocatalysts were uniformly spread to obtain a scalable photo-reactor by a relatively simple method, the so-called particle transfer method.^{4,5} Metal evaporation (in this study, the authors used gold), followed by

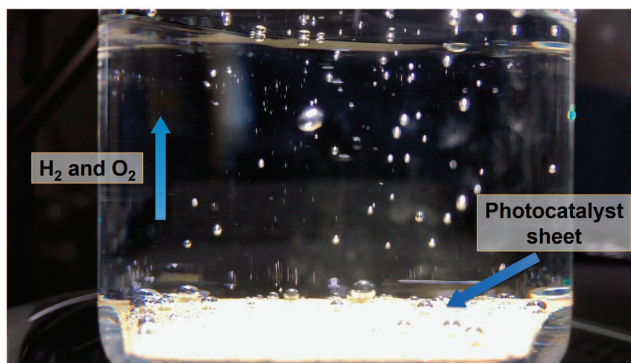


Figure 1 Photograph of a water-splitting reactor containing a photocatalytic sheet (bottom) under illumination.

the peeling off of the photocatalyst resulted in a very thin photocatalytic sheet. With further optimization of the annealing temperature for the improved Au-photocatalyst interface and the reaction temperature, an apparent quantum yield of 33% at 419 nm was achieved, and the overall solar to hydrogen efficiency reached 1.1% (the photo-reactor is shown in Figure 1).

Nevertheless, continuous efforts are necessary to achieve a benchmark STH efficiency of 10%. The absorption of more photons from the solar spectrum by choosing improved photocatalysts is one potential way to increase the overall efficiency, but the strength of the method reported here is that this method can be applied to other photocatalyst powders.

CONFLICT OF INTEREST

The author declares no conflict of interest.

- 1 Wang, Q., Hisatomi, T., Jia, Q., Tokudome, H., Zhong, M., Wang, C., Pan, Z., Takata, T., Nakabayashi, M., Shibata, N., Li, Y., Sharp, I. D., Kudo, A., Yamada, T. & Domen, K. Scalable water splitting on particulate photocatalyst sheets with a solar-to-hydrogen energy conversion efficiency exceeding 1%. *Nat. Mater.* **15**, 611–615 (2016).
- 2 Maeda, K., Teramura, K., Lu, D., Saito, N., Inoue, Y. & Domen, K. Noble-metal/Cr₂O₃ core/shell nanoparticles

as a cocatalyst for photocatalytic overall water splitting. *Angew. Chem. Int. Ed.* **45**, 7806–7809 (2006).

- 3 Takata, T., Pan, C., Nakabayashi, M., Shibata, N. & Domen, K. Fabrication of a core-shell-type photocatalyst via photodeposition of group IV and V transition metal oxyhydroxides: an effective surface modification method for overall water splitting. *J. Am. Chem. Soc.* **137**, 9627–9634 (2015).
- 4 Minegishi, T., Nishimura, N., Kubota, J. & Domen, K. Photoelectrochemical properties of LaTiO₂N electrodes prepared by particle transfer for sunlight-driven water splitting. *Chem. Sci.* **4**, 1120–1124 (2013).
- 5 Wang, Q., Lia, Y., Hisatomi, T., Nakabayashi, M., Shibata, N., Kubota, J. & Domen, K. Z-scheme water splitting using particulate semiconductors immobilized onto metal layers for efficient electron relay. *J. Catal.* **328**, 308–315 (2015).



This work is licensed under a Creative Commons Attribution

4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2016